



正电子湮没谱学研究氧离子注入AlN薄膜中缺陷对磁性影响

叶润 叶邦角

Effect of Defects on Magnetic Properties of O⁺-implanted AlN Films by Positron Annihilation Spectroscopy

YE Run, YE Bangjiao

在线阅读 View online: <https://doi.org/10.11804/NuclPhysRev.41.2023CNPC66>

引用格式:

叶润, 叶邦角. 正电子湮没谱学研究氧离子注入AlN薄膜中缺陷对磁性影响[J]. *原子核物理评论*, 2024, 41(1):498–503. doi: 10.11804/NuclPhysRev.41.2023CNPC66

YE Run, YE Bangjiao. Effect of Defects on Magnetic Properties of O⁺-implanted AlN Films by Positron Annihilation Spectroscopy[J]. *Nuclear Physics Review*, 2024, 41(1):498–503. doi: 10.11804/NuclPhysRev.41.2023CNPC66

您可能感兴趣的其他文章

Articles you may be interested in

低温硫化制备ZnS薄膜的物理性质研究

Physical Properties of ZnS Thin Films Prepared by Low-temperature Sulfidation

原子核物理评论. 2020, 37(3): 804–808 <https://doi.org/10.11804/NuclPhysRev.37.2019CNPC02>

Al-4%Ag合金中Ag原子偏析的低温正电子湮没参数研究

Study on Positron Annihilation Parameters of Low Temperature Segregation of Ag Atoms in Al-4%Ag Alloy

原子核物理评论. 2021, 38(1): 102–106 <https://doi.org/10.11804/NuclPhysRev.37.2020002>

北京大学1.7 MV串列静电加速器的离子注入/辐照实验系统

Ion Implantation/Irradiation System of 1.7 MV Tandem Accelerator at Peking University

原子核物理评论. 2021, 38(4): 410–415 <https://doi.org/10.11804/NuclPhysRev.38.2021058>

用于CSRe上¹⁶O⁵⁺离子精密激光光谱学实验的极紫外光子探测系统的研制

Development of an Ultraviolet Photon Detection System for Precision Laser Spectroscopy of Li-like ¹⁶O⁵⁺ Ion at the CSRe

原子核物理评论. 2022, 39(2): 224–231 <https://doi.org/10.11804/NuclPhysRev.39.2021042>

重离子辐照引起磁性隧道结功能失效类型及机理研究

Investigation of Types and Mechanisms of MTJ Function Failure Induced by Heavy Ion Irradiation

原子核物理评论. 2021, 38(1): 89–94 <https://doi.org/10.11804/NuclPhysRev.38.2020036>

基于Gate与Matlab的PET电子学仿真系统研究

Research on Electronic Simulation System of PET Based on Gate and Matlab

原子核物理评论. 2019, 36(4): 447–455 <https://doi.org/10.11804/NuclPhysRev.36.04.447>

Article ID: 1007-4627(2024)01-0498-06

Effect of Defects on Magnetic Properties of O^+ -implanted AlN Films by Positron Annihilation Spectroscopy

YE Run¹, YE Bangjiao^{2,†}

(1. School of Physics and Electronic Engineering, Yancheng Teachers University, Yancheng 224007, Jiangsu, China;

2. State Key Laboratory of Particle Detection and Electronics, University of Science and Technology of China, Hefei 230026, China)

Abstract: Room-temperature ferromagnetism is observed in the O^+ -implanted AlN films with O^+ doses of $5 \times 10^{16} \text{ cm}^{-2}$ (AlN: $O_{5 \times 10^{16}}$) and $2 \times 10^{17} \text{ cm}^{-2}$ (AlN: $O_{2 \times 10^{17}}$). The observed magnetic anisotropy indicates that the ferromagnetism is attributed to the intrinsic properties of O^+ -implanted AlN films. The out-of-plane saturation magnetization (M_s) of the AlN: $O_{5 \times 10^{16}}$ is about 0.68 emu/g, much higher than that of AlN: $O_{2 \times 10^{17}}$, 0.09 emu/g, which is due to the excessively high O^+ dose made more O^+ ions occupy adjacent Al^{3+} positions in forms of antiferromagnetic coupling. Doppler broadening of positron annihilation radiation measurements demonstrate the existence of Al vacancies in the O^+ -implanted AlN films. The first-principles calculations suggest that the ferromagnetism originates mainly from the Al vacancies. Meanwhile, the formation of divacancies or vacancy clusters by high concentrations of Al vacancies will lead to the transformation of $V_{Al}-V_{Al}$ coupling from ferromagnetism to antiferromagnetism, ultimately weakening the ferromagnetism of the sample.

Key words: positron annihilation spectroscopy; ion implantation; semiconductors; ferromagnetism

CLC number: O77⁺1 **Document code:** A **DOI:** 10.11804/NuclPhysRev.41.2023CNPC66

0 Introduction

AlN, a wide-bandgap III-V semiconductor, has attracted much attention in the last decade for its high thermal conductivity, high electron mobility, and good chemical stability^[1-2]. The induced magnetism in AlN makes it possible to manipulate the charge and spin degrees of freedom of an electron in AlN simultaneously. Thus, AlN is a promising candidate in spintronics^[3] and becomes a diluted magnetic semiconductor (DMS) when doped with transition metals inducing ferromagnetism^[4-6].

Recently, ferromagnetism was observed in AlN with non-magnetism dopants such as Cu^[7], Mg^[8], and C^[9]. As the most common element, Oxygen can easily become an impurity in the sample, thus affecting the properties of sample. However, the magnetic O-doped AlN has rarely been investigated^[10]. Generally speaking, AlN films doped with non-magnetism dopants or transition metals often contain a large number of defects, and the defects are not evenly distributed, especially doping by ion implanta-

tion. It's of great importance for the origin of ferromagnetism in AlN DMS films to probe the defect structure and identify the defect types.

Positron annihilation spectroscopy has turned out to be a unique method to investigate nanometer-scaled defects in materials^[11-12]. By controlling the energy of incident positron, depth profile of samples can be obtained by detecting the annihilation gamma rays. A high-purity Ge detector was applied to detect γ rays produced by the positron annihilation to reconstruct the Doppler broadening of annihilation radiation (DBAR) spectrum. The obtained DBAR spectrum was characterized by S and W parameters. The S parameter is defined as the ratio of central area of annihilation peak ($511 \pm 0.81 \text{ keV}$) to the total peak area, reflecting the information of positron annihilation with low-momentum electrons (valence electron or conduction electron). The W parameter is the ratio of wing area ($505.92 \sim 509.16 \text{ keV}$, $512.84 \sim 516.08 \text{ keV}$) to the total peak area, which reflects the information of positron annihilation with high-momentum electrons (core electrons). When

Received date: 01 Sep. 2023; **Revised date:** 24 Feb. 2024

Foundation item: National Key R&D Program of China (2019YFA0210000); National Natural Science Foundation of China (12305333); State Key Laboratory of Particle Detection and Electronics (SKLPDE-KF-202114); Fundamental Research Program of Yancheng City (YCBK2023061); Innovation and Entrepreneurship Doctors of Jiangsu Province (JSSCBS20211148); Natural Science Foundation of Jiangsu Province (BK20220699)

Biography: YE Run(1991-), mail, Huanggang, Hubei Province, Lecturer, working on positron annihilation spectroscopy; E-mail: yer@yctu.edu.cn

† Corresponding author: YE Bangjiao, E-mail: bjye@ustc.edu.cn

positrons are captured by vacancy-type defects in samples, the S parameter increases and W parameter decreases due to the higher fraction of valence electrons around defects than those in defect-free regions. Taking advantages of DBAR measurements, the defect distribution of AlN films can be obtained. In this work, we prepared O⁺-doped AlN films by ion implantation and investigated the structural and magnetic properties of O⁺-implanted AlN films.

1 Experiment

1- μm thick unintentionally doped AlN films (marked as as-grown AlN) prepared on c -plane (0001) sapphire substrates ($\sim 500 \mu\text{m}$ thick) by hydride vapor phase epitaxy were purchased from Hefei Kejing Materials Technology Co., Ltd. The AlN:O_{5 \times 10¹⁶} and AlN:O_{2 \times 10¹⁷} (the subscript denotes the dose of implanted O⁺ ions in cm⁻²) were obtained by implanting O⁺ ions with the energy of 80 keV into two as-grown AlN films. The ion implantation experiments were performed using an ion implanter at room temperature. The base pressure of implantation chamber was about 2×10^{-4} Pa.

X-ray diffraction (XRD) measurements were conducted by using an X-ray diffractometer (PANalytical X'Pert PRO MPD) in Bragg-Brentano geometry (240 mm radius) with Cu-K α radiation ($\lambda = 1.5406 \text{ \AA}$). The Raman spectra were measured at room temperature by using a Lab-RamHR Evolution Raman system with an Ar⁺ ion laser (wavelength centered at 514.5 nm) in backscattering geometry as an excitation source. The DBAR measurements were performed using a slow positron beam with a variable energy from 0.25 to 25 keV at the University of Science and Technology of China. The magnetic properties of AlN films were investigated using a Superconducting Quantum Interference Device (MPMS3, Quantum Design) with an accuracy of 10^{-8} emu. The magnetic hysteresis loop measurements were carried out at room temperature with the magnetic field parallel and perpendicular to the plane of the samples, respectively.

2 Results and discussion

The crystal structures of the AlN samples were investigated by XRD. The XRD spectra were normalized with respect to the intensity of the (0006) peak of the sapphire substrate for the as-grown AlN sample. As shown in Fig. 1, the typical (002) peaks of AlN are observed, which can be indexed to h-AlN. No peaks related to metallic Al are found in the AlN patterns. As shown in the inset of Fig. 1, the intensity of (002) peak was reduced after ion implantation, indicating that the ion implantation process introduced lots of lattice defects in AlN:O_{5 \times 10¹⁶} and AlN:O_{2 \times 10¹⁷}. The XRD results of the AlN samples are shown in Table 1. The AlN

(002) peak shifts towards larger 2θ after implantation, suggesting a lattice contraction along the c -axis for AlN microcrystals in AlN:O_{5 \times 10¹⁶} and AlN:O_{2 \times 10¹⁷}, which is likely attributed to the substitution of N⁺ or Al³⁺ by the O⁺ ions due to the smaller covalent radius of O^[13].

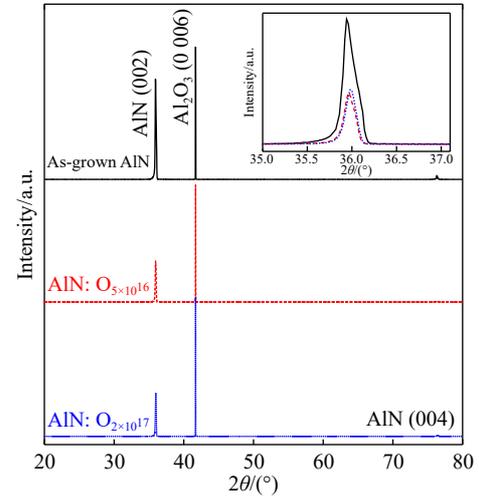


Fig. 1 XRD patterns of as-grown AlN, AlN:O_{5 \times 10¹⁶}, and AlN:O_{2 \times 10¹⁷}. The inset shows the magnification of AlN (002) peaks.

Table 1 XRD results of the AlN samples.

Sample	Peak positron/(°)	c parameter/ \AA
	(002)	
as-grown AlN	35.95	4.992
AlN:O _{5\times10¹⁶}	35.96	4.991
AlN:O _{2\times10¹⁷}	35.98	4.988

The Raman spectra of as-grown AlN, AlN:O_{5 \times 10¹⁶}, and AlN:O_{2 \times 10¹⁷} are shown in Fig. 2. For as-grown AlN, first-order phonon modes located at 250 cm^{-1} [E_2 (low)], 659 cm^{-1} [E_2 (high)], and 889 cm^{-1} [A_1 (LO)] were observed, which are in good agreement with the values measured for the AlN films^[14–15]. Other five peaks (marked as asterisks) are attributed to vibrational modes from the sapphire substrate.

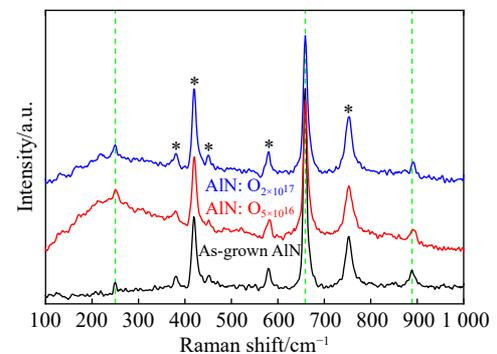


Fig. 2 Raman spectra for as-grown AlN, AlN:O_{5 \times 10¹⁶}, and AlN:O_{2 \times 10¹⁷}. The asterisks represent vibrational modes related to the sapphire substrate. The green dotted lines represent the first-order phonon modes of AlN E_2 (low), E_2 (high), and A_1 (LO), respectively. (color online)

For AlN: O_{5×10¹⁶} and AlN: O_{2×10¹⁷}, the E₂ (high) peaks located at 659 cm⁻¹ were also seen clearly in Fig. 2. The full width at half maximum (FWHM) of E₂ (high) peak for as-grown AlN, AlN: O_{5×10¹⁶}, and AlN: O_{2×10¹⁷} are about 7.4, 11.1, and 12.1 cm⁻¹, respectively. The E₂ (high) peak broadens after O⁺ implantation, suggesting that there are high-density defects in AlN: O_{5×10¹⁶} and AlN: O_{2×10¹⁷}. With increasing O⁺ concentration, the intensity of E₂ (high) peak decreases, and the peak becomes asymmetric, indicating the lattice distortion of AlN wurtzite structure. What's more, the E₂ (low) and A₁ (LO) components in AlN: O_{5×10¹⁶} and AlN: O_{2×10¹⁷} disappear, broad bands emerge instead. In general, the broadening in Raman band and absence of local vibrational modes are associated with the lattice disorder, defects, and substitutional impurities, which can lead to photon confinement and loss of periodicity^[16–17]. The vacancies and substitution of O⁺ ions for N⁺ or Al³⁺ ions are responsible for the changes in peak shape mentioned above.

Figure 3(a) shows the S parameters versus positron energy (S–E curves) measured for AlN films. For as-grown AlN, the positron energy of 0~2 keV is corresponding to the surface layer. The large S parameter is due to the positron annihilations and formation of positronium atoms at the surface^[18]. In the surface layer, S parameters decrease with increasing positron energy. The S values satur-

ate at positron energy of 2~10 keV, indicating that positrons annihilate in the AlN layer. The obtained bulk S parameter (S_b) for as-grown AlN is about 0.439. Then the S parameters decrease in the energy region E > 10 keV due to the annihilation of positrons in the sapphire substrate. Compared to as-grown AlN, the O⁺-implanted AlN films show much higher S parameters in the whole energy range, which is attributed to the annihilation of positrons in vacancy-type defects introduced by O⁺ implantation. The effective positron trapping centers in AlN are Al-related vacancies (negative charges). The defect types in AlN: O_{5×10¹⁶} and AlN: O_{2×10¹⁷} can be determined by the S parameters. The S values for the defect layer (S_d) in AlN: O_{5×10¹⁶} (AlN: O_{2×10¹⁷}) is 0.461 (0.454), then the value of S_d/S_b is approximately 1.050 (1.034), which indicates the implantation-induced defects in AlN: O_{5×10¹⁶} and AlN: O_{2×10¹⁷} are probably monovacancies (V_{Al}) or divacancies according to previous reports^[19–20].

To further investigate the positron annihilation characteristics in the AlN films, the S–E curves were fitted using VEPFIT software^[21] to resolve the defect depth profiles and depth structures of implanted AlN layers. The S parameter measured at different positron energy E can be expressed by the following formula:

$$S(E) = S_s F_s(E) + \sum_{i=1}^n S_i F_i(E), \quad (1)$$

where S_s and S_i are the S parameters to the positrons annihilated at the surface and in the ith layer, respectively; while, F_s and F_i denote the fraction of positrons annihilated at the surface and in the ith layer with the relation of F_s(E) + ∑_{i=1}ⁿ F_i(E) = 1, respectively. As shown in Fig. 3(a), the solid lines are in accord with the experimental data. According to the previous work^[22], the region exposed to annihilated positrons was divided into two blocks for as-grown AlN, and three blocks for AlN: O_{5×10¹⁶} (AlN: O_{2×10¹⁷}), respectively. The defect depth profiles for the AlN films are shown in Fig. 3(b). In the first block of ~60 nm, AlN: O_{5×10¹⁶} and AlN: O_{2×10¹⁷} exhibit high S values due to the ion implantation and high O⁺ concentration. However, the S value of AlN: O_{5×10¹⁶} is much higher than that of AlN: O_{2×10¹⁷}, which was attributed to the reverse diffusion of implanted ions. In the implantation procedure, vacancy defect was formed, some O⁺ ions diffused towards the surface of AlN films and then gathered. At the lower implantation doses, less O⁺ ions occupied Al vacancies while more O⁺ ions occupied Al vacancies at higher doses, leading to more vacancy defects at lower implantation doses than higher doses before 60 nm of the film thickness. This anomalous results have also been observed in C⁺-implanted AlN films^[9]. In the second block of ~350 nm, high S values for AlN: O_{5×10¹⁶} and AlN: O_{2×10¹⁷} are owing to the Al-related

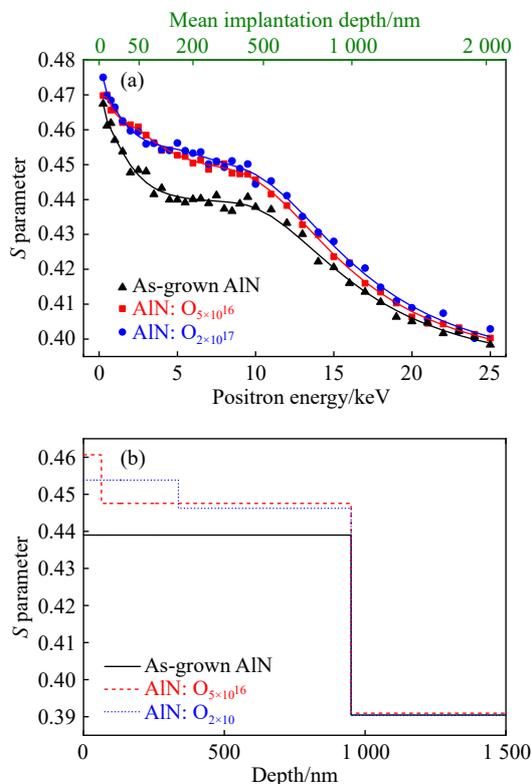


Fig. 3 (a) The parameter S as a function of positron energy (E) for the samples. Solid lines are fitted to the experimental data by VEPFIT software. (b) S depth distributions obtained from analysis of S–E curves for the samples.

vacancies. The third block of ~ 950 nm depth corresponds to the AlN thickness, the S values tend to be the same due to the annihilation of vast majority of positrons in the sapphire substrate.

In order to character the change of vacancy type, S - W analysis were performed for all AlN films as shown in Fig. 4. The S - W data for positron energies below 2 keV were subtracted. The fitting curves of the S - W data for the as-grown AlN, AlN:O_{5×10¹⁶}, and AlN:O_{2×10¹⁷} are straight lines and approximately overlapped, indicating that these samples contain the same types of defects. Therefore, increasing the dose of O⁺ ions increases the density of the Al-related vacancies but does not change the defect type.

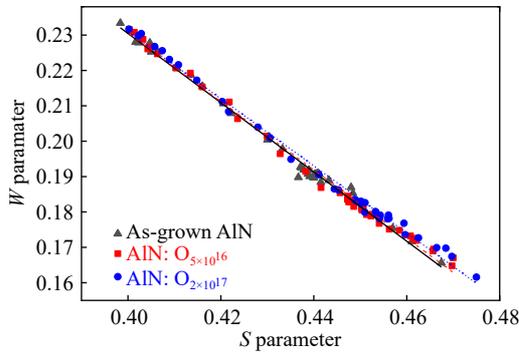


Fig. 4 Plots of S vs W for the samples. The black solid, red dashed, and blue dotted lines are fits to the S - W data for the as-grown AlN, AlN:O_{5×10¹⁶}, and AlN:O_{2×10¹⁷}, respectively. (color online)

The variations of magnetization (M) as a function of magnetic field (H) for AlN:O_{5×10¹⁶} and AlN:O_{2×10¹⁷} by applying magnetic field perpendicular (\perp) to the sample plane are shown in Fig. 5(a). In our previous work, as-grown AlN exhibited an almost zero hysteresis phenomenon and showed diamagnetic character, indicating the absence of magnetic impurities in the as-grown AlN^[9]. The ferromagnetic behavior has been observed for AlN:O_{5×10¹⁶} and AlN:O_{2×10¹⁷}. The saturation magnetization (M_s) of the AlN:O_{5×10¹⁶} is about 0.68 emu/g, much higher than that of AlN:

O_{2×10¹⁷}, 0.09 emu/g. This might be due to the excessively high O⁺ dose would increase the number of O⁺ ions occupying adjacent Al³⁺ positions, resulting in antiferromagnetic coupling^[7, 23]. This finding is consistent with the DBAR results. The magnetic properties of AlN:O_{5×10¹⁶} were measured by applying magnetic field parallel ($//$) and perpendicular (\perp) to the sample plane, respectively, as shown in Fig. 5(b). Much stronger ferromagnetism of AlN:O_{5×10¹⁶} are observed in the perpendicular direction, 0.68 emu/g than in parallel, 0.29 emu/g. The magnetic anisotropy can be considered as an evidence of intrinsic ferromagnetism in O⁺-implanted AlN films^[24].

To further investigate the origin of the ferromagnetism in O⁺-implanted AlN films, we calculated their electronic and magnetic properties using the DFT methods^[9]. For the supercell containing a single Al vacancy, the total magnetic moment is 3.00 μ_B . Furthermore, the calculated total energy of the spin-polarized state is approximately 556 meV lower than that of the non-spin-polarized state, indicating that single Al vacancy prefers the spin-polarized state. The magnetic coupling of Al divacancies ($V_{Al}-V_{Al}$) with different distances are also investigated^[25]. The results suggest that the energy difference between antiferromagnetic and ferromagnetic phases rises sharply with the distance increase of two Al vacancies, leading to the crucial transformation of $V_{Al}-V_{Al}$ coupling from antiferromagnetism to ferromagnetism. When the $V_{Al}-V_{Al}$ distance is less than 9.96 Å, the magnetic coupling between them is tend to form antiferromagnetic interaction. Thus, for ion-implantation with higher dose, divacancies or vacancy clusters will weaken the ferromagnetism of AlN films, which is consistent with the results of magnetic measurements. According to the above results, it is proposed that the intrinsic ferromagnetism in the O⁺-implanted AlN films is related to the Al vacancies. The O⁺ ions occupying the adjacent Al³⁺ positions and Al divacancies or vacancy clusters jointly play important roles in regulating the magnetic property in the forms of antiferromagnetic alignment.

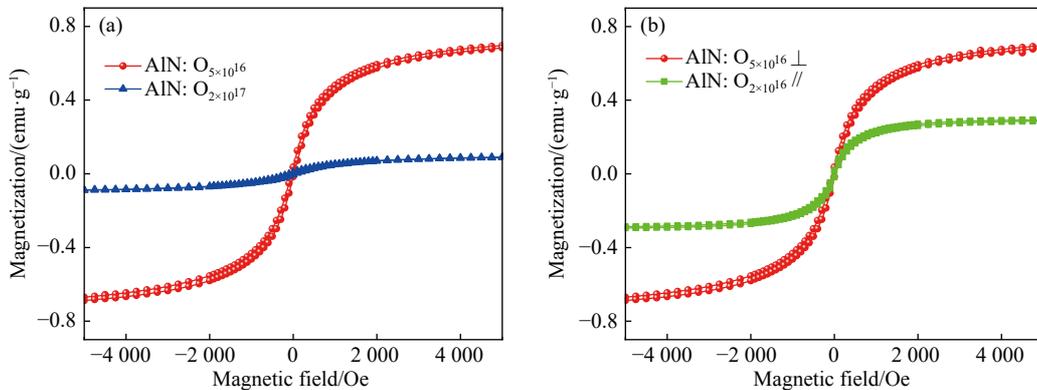


Fig. 5 (a) Room-temperature out-of-plane M - H loops for AlN:O_{5×10¹⁶} and AlN:O_{2×10¹⁷}. The diamagnetic background signals were subtracted. The magnetization values were normalized by accounting for the masses of the AlN films. (b) Magnetic anisotropy of AlN:O_{5×10¹⁶}. (1 Oe=1000/(4 π) A/m)

3 Summary

Room-temperature ferromagnetism was observed in the O^+ -implanted AlN films. The M_s was decreased with increasing O^+ dose, due to the excessively high O^+ dose made more O^+ ions occupy adjacent Al^{3+} positions in the forms of antiferromagnetic coupling, which was determined by the DBAR experiments. The first-principles calculations and DBAR experiments revealed that the ferromagnetism originates mainly from the Al vacancies. The formation of divacancies or vacancy clusters by high concentrations of Al vacancies will lead to the transformation of $V_{Al}-V_{Al}$ coupling from ferromagnetism to antiferromagnetism, ultimately weakening the ferromagnetism of the sample. This work reveals the roles of cation vacancies and substitute atoms in ferromagnetism within the nonmagnetic element-implanted DMSs. Meanwhile, it demonstrates once more that the positron is a very useful probe for nanometer-scaled defects in materials and will be widely used in the research of semiconductors.

Acknowledgments This work was supported by the National Key R&D Program of China (Grant No. 2019YFA0210000), the National Natural Science Foundation of China (Grant No. 12305333), the Fundamental Research Program of Yancheng City (Grant No. YCBK2023061), the State Key Laboratory of Particle Detection and Electronics (Grant No. SKLPDE-KF-202114), the Innovation and Entrepreneurship Doctors of Jiangsu Province (Grant No. JSSCBS20211148), and the Natural Science Foundation of Jiangsu Province (Grant No. BK20220699).

References:

- [1] ZANG H, SUN X, JIANG K, et al. *Advanced Science*, 2021, 8(18): 2100100.
- [2] LIU F, WANG T, GAO X, et al. *Science Advances*, 2023, 9(31): eadf8484.
- [3] WOLF S, AWSCHALOM D, BUHRMAN R, et al. *Science*, 2001, 294(5546): 1488.
- [4] FRAZIER R, STAPLETON J, THALER G, et al. *Journal of Applied Physics*, 2003, 94(3): 1592.
- [5] KUMAR D, ANTIFAKOS J, BLAMIRE M, et al. *Applied Physics Letters*, 2004, 84(24): 5004.
- [6] ZHU Z, OU Z, CHEN Y, et al. *Journal of Alloys and Compounds*, 2023, 170986.
- [7] RAN F Y, SUBRAMANIAN M, TANEMURA M, et al. *Applied Physics Letters*, 2009, 95(11): 112111.
- [8] XU Y, YAO B, LIU D, et al. *CrystEngComm*, 2013, 15(17): 3271.
- [9] YE R, LIU J, ZHANG H, et al. *Applied Physics Letters*, 2019, 115(26): .
- [10] NATH D, CHAKRAVARTY S, GUPTA M, et al. *Journal of Alloys and Compounds*, 2023, 171727.
- [11] TUOMISTO F, MAKKONEN I. *Reviews of Modern Physics*, 2013, 85(4): 1583.
- [12] AGARWAL S, LIEDKE M, JONES A, et al. *Science Advances*, 2020, 6(31): eaba8437.
- [13] LIU C, MENSCHING B, VOLZ K, et al. *Applied Physics Letters*, 1997, 71(16): 2313.
- [14] DAVYDOV V Y, KITAEV Y E, GONCHARUK I, et al. *Phys Rev B*, 1998, 58(19): 12899.
- [15] SOARES M, LEITÃO J, DA SILVA M, et al. *Optical Materials*, 2011, 33(7): 1055.
- [16] LUGHI V, CLARKE D R. *Applied Physics Letters*, 2006, 89(24): 241911.
- [17] SHAH A, AHMAD J, AHMAD I, et al. *Applied Surface Science*, 2014, 317: 262.
- [18] ZHANG B, YAO B, LI Y, et al. *Applied Physics Letters*, 2011, 99(18): 182503.
- [19] UEDONO A, ITO K, NAKAMORI H, et al. *Journal of Applied Physics*, 2007, 102(8): 084505.
- [20] LI X, CHEN Z, LIU C, et al. *Journal of Applied Physics*, 2015, 117(8): 085706.
- [21] VAN VEEN A, SCHUT H, CLEMENT M, et al. *Applied Surface Science*, 1995, 85: 216.
- [22] OKUMURA H, UEDONO A. *Japanese Journal of Applied Physics*, 2023, 62(2): 020901.
- [23] XIONG J, GUO P, GUO F, et al. *Materials Letters*, 2014, 117: 276.
- [24] VENKATESAN M, FITZGERALD C, LUNNEY J, et al. *Phys Rev Lett*, 2004, 93(17): 177206.
- [25] YE R, LIU J, ZHANG H, et al. Room Temperature Ferromagnetism Induced by Al-vacancy in N^+ Implanted AlN Films[Z].

正电子湮没谱学研究氧离子注入 AlN 薄膜中缺陷对磁性影响

叶润¹, 叶邦角^{2,†}

(1. 盐城师范学院物理与电子工程学院, 江苏 盐城 224007;

2. 中国科学技术大学核探测与核电子学国家重点实验室, 合肥 230026)

摘要: 在氧离子注入的 AlN 薄膜 AlN:O_{5×10¹⁶} (剂量为 5×10¹⁶ cm⁻²) 和 AlN:O_{2×10¹⁷} (剂量为 2×10¹⁷ cm⁻²) 中观察到了室温铁磁性。所观察到的磁各向异性表明, 氧离子注入的 AlN 薄膜中铁磁性是本征特性。在垂直于样品平面的外加磁场下, AlN:O_{5×10¹⁶} 中的饱和磁化强度约为 0.68 emu/g, 高于 AlN:O_{2×10¹⁷} 中的饱和磁化强度 0.09 emu/g。这是由于过高的氧离子剂量使得更多的氧离子占据相邻的 Al 离子位置, 导致了反铁磁耦合的出现。正电子湮没多普勒展宽谱表明在氧离子注入的 AlN 薄膜中存在大量的 Al 空位。第一性原理计算表明氧离子注入的 AlN 薄膜中的铁磁性主要来源于 Al 空位, 而高浓度的 Al 空位形成双空位或空位团将会使得 AlN 样品从铁磁性到反铁磁性转变, 最终使样品的铁磁性减弱。

关键词: 正电子湮没谱学; 离子注入; 半导体; 铁磁性

收稿日期: 2023-09-01; 修改日期: 2024-02-24

基金项目: 国家重点研发计划“纳米科技”重点专项资助项目(2019YFA0210000); 国家自然科学基金资助项目(12305333); 核探测与核电子学国家重点实验室开放课题资助项目(SKLPDE-KF-202114); 盐城市基础 Research 计划资助项目(YCBK2023061); 江苏省“双创博士”计划资助项目(JSSCBS20211148); 江苏省自然科学基金资助(BK20220699)

† 通信作者: 叶邦角, E-mail: bjye@ustc.edu.cn